

TR1110 TCR RESIN SYSTEM



Technical Data Sheet

TR1110 is a halogen free, flame-retardant thermosetting epoxy matrix resin system that meets UL94-V1 at 3.2 mm thickness, 90° fiber orientation. This prepreg system has excellent mechanical properties and long room temperature shelf life.

Available Prepreg Product Formats

- Tow (roving)
- Woven form/fabric

Shelf Life

- 6 months at 24°C (75°F)
- 3 months at 32°C (90°F)

Benefits/ Features

- Long shelf life
- Tailored flow and tack levels
- Meets UL-94 V-1 at 3.2 mm thickness, 90° fiber orientation

Cure Conditions

Curing cycle for composite parts <6.35 mm or 0.25 inches in thickness

- Ramp ≤ 2.78°C/min to 177°C (350°F)
- Hold 1 hour at 177°C
- Ramp ≤ 2.78°C/min ≤ 66°C (150°F)

Thick composite parts (>6.35 mm or 0.25 inches) will require a modified cure cycle. Please contact TCR Composites for more information.

Cured Neat Resin Physical Properties*


Properties	Metric	English	Test Method
Density	1.39 g/cc	0.0502 lbs/in ³	ASTM D 792
Tensile Strength	53 MPa	7.7 kpsi	ASTM D 638
Tensile Modulus	4.20 GPa	610 kpsi	ASTM D 638
Strain (% Elongation)	1.39%		ASTM D 638
Fracture Toughness – K _{IC}	0.6190 MPa*m ^{1/2}	562.6 psi*in ^{1/2}	ASTM D 5045
DMA – Dry Glass Transition			
Glass Transition – E" Peak	160°C	320°F	ASTM E 1640
Glass Transition – E' Onset	155°C	311°F	ASTM E 1640
Glass Transition – Tan δ Peak	175°C	348°F	ASTM E 1640
DMA – Wet Glass Transition**			
Glass Transition – E" Peak	118°C	244°F	ASTM E 1640
Glass Transition – E' Onset	112°C	234°F	ASTM E 1640
Glass Transition – Tan δ Peak	124°C	255°F	ASTM E 1640
Water Absorption**	3.3%		ASTM D 570

*Cure cycle: 1 hour at 177°C

**DMA wet glass transition and water absorption measured after 24-hour water boil

Resin Cure Viscosity

Parallel-plate rheometer

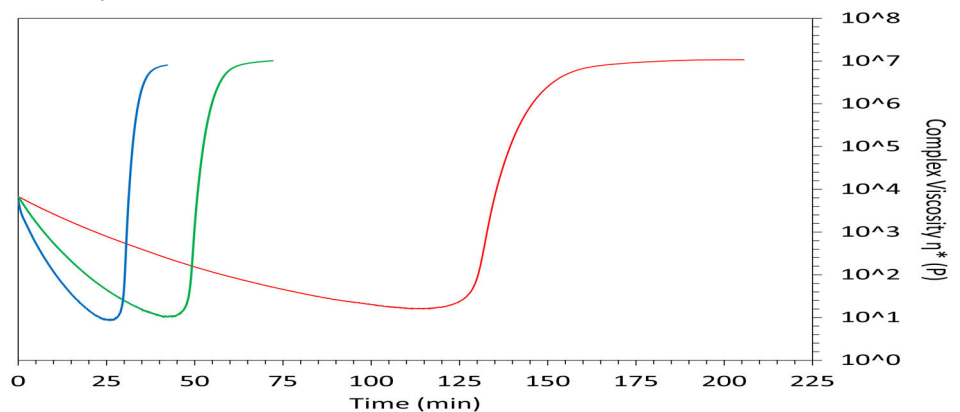

0.56°C (1°F)/min—Min η*: 15.72 P, 101°C (214°F)

1.67°C (3°F)/min—Min η*: 10.15 P, 107°C (225°F)

2.78°C (5°F)/min—Min η*: 8.17 P, 116°C (241°F)

(η*) Time to Viscosity Minimum: {(Min η* Temperature (°C/°F) – (38°C/100°F)} ÷ {(°C/°F)/min}

TCR Composites

219 North 530 West, Ogden, Utah 84404 USA

1-800-827-3746

1-801-622-3800

sales@tcrcomposites.com | www.tcrcomposites.com

TDS-RD-0110-R005-TR1110

TR1110 TCR RESIN SYSTEM



Technical Data Sheet

Cure Profiles

Option	Ramp Up	Hold Temperature	Hold Time (hours)	Ramp Down
1	≤2.78°C/min (5°F/min)	177°C (350°F)	1	≤2.78°C/min (5°F/min) to 66°C (150°F) or less
2		166°C (330°F)	2	
3		154°C (310°F)	4	

All values presented within this technical data sheet are expected ranges based on actual test data. Since values are dependent on specimen preparation and test method, TCR Composites cannot guarantee that these properties will be obtained in all cases. Data should be used only as an indication, since part or component properties are highly dependent on user process and design. It is recommended that end users determine the suitability of this material for each application through their own testing and evaluation.

TCR Composites

219 North 530 West, Ogden, Utah 84404 USA

1-800-827-3746

1-801-622-3800

sales@tcrcomposites.com | www.tcrcomposites.com

TDS-RD-0110-R005-TR1110

Page 2 of 2